



Cite this: *Polym. Chem.*, 2015, **6**, 5110

Multiple hydrogen bonding mediates the formation of multicompartment micelles and hierarchical self-assembled structures from pseudo *A-block-(B-graft-C)* terpolymers†

Yi-Chen Wu,^{a,b} Bishnu Prasad Bastakoti,^b Malay Pramanik,^b Yusuke Yamauchi*^b and Shiao-Wei Kuo*^a

In this study, we report a simple but effective method for preparing various multi-compartment micelle structures: poly(styrene-*b*-4-vinylbenzyl triazolylmethyl methylthymine) (PS-*b*-PVBT) diblock copolymers blended with the adenine-terminated poly(ethylene oxide) (A-PEO) homopolymer to obtain pseudo *A-b-(B-g-C)*-type terpolymers stabilized through thymine–adenine (T–A) multiple hydrogen bonding interactions between PVBT and A-PEO segments in DMF (*N,N*-dimethylformamide) common solvent after the addition of H₂O or MeCN selective solvent. Transmission electron microscopy revealed several different multi-compartment micelle structures—raspberry-like spheres, core–shell–corona spheres, core–shell–corona cylinders, nanostructured vesicles, onion-like structures, segmented worm-like cylinders, and woodlouse-like structures—upon varying the molecular weight of the PS-*b*-PVBT block segments and the concentration of the selective solvent. Thus, we could induce changes in the multi-compartment micelle structures, similar to those of ABC miktoarm star terpolymers, through simple blending of PS-*b*-PVBT block copolymers with an A-PEO homopolymer.

Received 6th May 2015,
Accepted 12th June 2015

DOI: 10.1039/c5py00663e

www.rsc.org/polymers

Introduction

Block copolymers can lead to the formation of self-assembled micelle structures with an insoluble hydrophobic block core surrounded by a hydrophilic block shell since such systems can display fascinating nanostructures (*e.g.* spherical, cylindrical, and vesicular micelles) of high stability. They possess much interest for the delivery of drugs, genes and proteins.^{1,2} The hydrophilic shell can stabilize the hydrophobic core as an interface between the hydrophobic region and the aqueous phase. In addition, the hydrophobic block core can act as a carrier compartment to accommodate predominantly hydrophobic drugs.³

The self-assembly of more complex macromolecules (*e.g.* ABC linear triblock terpolymers) into multi-compartment micelles has also attracted much interest in recent years.^{4–9}

With an appropriate selective solvent, the three linear individual block segments of an ABC linear triblock terpolymer can undergo core–shell–corona compartment aggregation.⁴ In addition, the ability to form ABC miktoarm star terpolymers in a selective solvent for one block segment is quite an attractive proposition. Here, C usually represents the hydrophilic block segment and A and B represent different hydrophobic blocks.^{10–14} The overall size and shape of the multi-compartment micelles are strongly dependent on the internal arrangement of hydrophobic components formed between the A and B block segments. A variety of multi-compartment micelles have been prepared, including raspberry-like, hamburger-like, segmented worm-like, and nanostructured vesicle micelles, through changes in the relative block segment ratios and architectures.⁴ The advantage to using ABC miktoarm star terpolymers is suppressed formation of core–shell–corona structures because these three block segments should meet along a curve in space among the three interfacial energies and the relative block lengths.⁴ In addition to ABC triblock terpolymers, *A-block-(B-graft-C)* or dendritic–amphiphilic copolymers have also been used to fabricate hierarchical multi-compartment micelles.¹⁵

Nevertheless, the syntheses of ABC linear triblock copolymers, ABC miktoarm star terpolymers, and *A-block-(B-graft-C)* terpolymers can be difficult and time-consuming. Another

^aDepartment of Materials and Optoelectronic Science, Center for Nanoscience and Nanotechnology, National Sun Yat-Sen University, Kaohsiung, 804, Taiwan. E-mail: kuosw@faculty.nsysu.edu.tw


^bWorld Premier International (WPI) Research Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), 1-1 Namiki, Tsukuba, Japan. E-mail: Yamauchi.Yusuke@nims.go.jp

† Electronic supplementary information (ESI) available: GPC, ¹H NMR, SAXS and TEM images of PS-*b*-PVBT diblock copolymer. See DOI: 10.1039/c5py00663e

approach for the preparation of multi-compartment micelles is through blending of two or more different block copolymers. Blending the polymers in various ratios is a relatively simple method for systematically varying micelle structures without the need for tedious syntheses of multi-block copolymers of various compositions.^{16–18} For example, Webber *et al.* reported core–shell–corona spherical micelles through the blending of *A-b-B* and *B-b-C* diblock copolymers; their B block segment displayed pH-dependent water-solubility.¹⁹ Zhu *et al.* described the transformation of spherical core–shell–corona micelles to cylindrical core micelles upon blending amphiphilic *A-b-B* copolymers with several different hydrophobic *B-b-C* diblock copolymers.²⁰ Lodge *et al.* reported various multi-compartment micelles that formed when blending *A-b-B* copolymers with star-like ABC triblock copolymers.²¹ Pochan *et al.* blended ACB and ABD triblock terpolymers to form multi-compartment micelle structures.²² As mentioned above,^{19–22} these multi-compartment micelles are usually produced by blending diblock or triblock copolymers. Because the syntheses of block copolymers are generally difficult and time-consuming, using

noncovalently connected micelles (NCCMs) to prepare self-assembled micelles is attractive from complementary homopolymer pairs.^{23–28} Jiang *et al.* reported NCCMs from a “block copolymer-free” method using complementary homopolymer pairs.²³ Terminally functionalized homopolymers blended with side-chain-functionalized homopolymers or copolymers form “graft-like” copolymers stabilized through hydrogen bonding in common solvents, for example, carboxyl-terminated polystyrene (PS) oligomers interacting with poly(4-vinylpyridine) (P4VP), stabilized through COOH...pyridine hydrogen bonding.²⁵

In this study, we introduce a very simple route for the preparation of various multi-compartment micelles: blending hydrophobic *A-b-B* diblock copolymers with terminally functionalized hydrophilic C homopolymers (*i.e.* through blending of only the diblock copolymer with the homopolymer). We synthesized poly(styrene-*b*-4-vinylbenzyl triazolylmethyl methylthymine) (PS-*b*-PVBT) by using nitroxide-mediated radical polymerization to prepare poly(styrene-*b*-4-vinylbenzyl azide) (PS-*b*-PVBN₃), followed by click chemistry

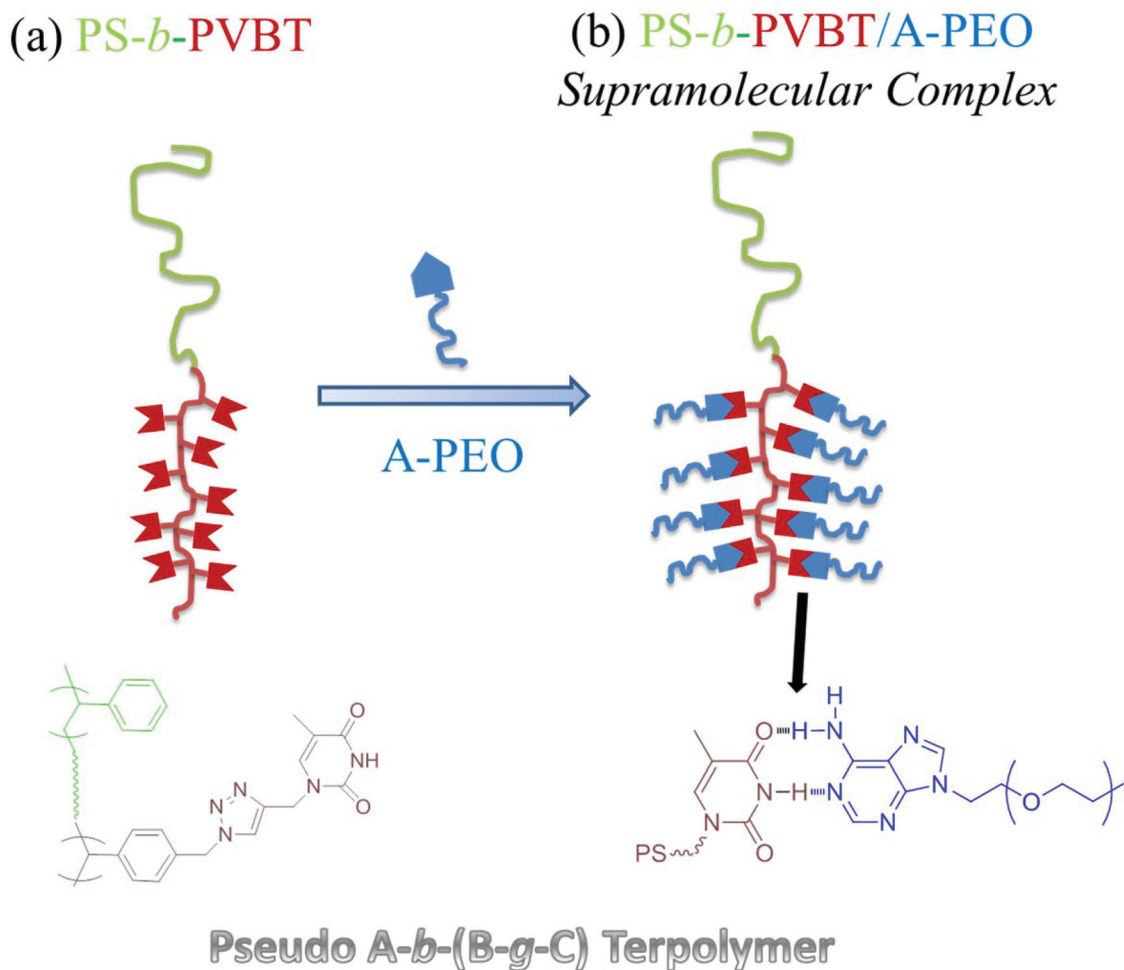

Scheme 1 Cartoon representations of (a) PS-*b*-PVBT and (b) the supramolecular complex PS-*b*-PVBT/A-PEO, with the chemical structure of the interaction between the T and A units.

with propargyl-thymine (PT) to obtain the thymine (T)-containing PS block copolymers (Scheme S1†). We employed an adenine (A)-terminated poly(ethylene oxide) (A-PEO) homopolymer (Scheme S2†) to induce bio-inspired DNA-like multiple hydrogen bonds (between the A and T units). The resulting PS-*b*-PVBT/A-PEO supramolecular complexes were stabilized through these strong noncovalent interactions (Scheme 1), behaving as pseudo A-*b*-(B-*g*-C) terpolymers. To prepare the multi-compartment micelles, we first dissolved the PS-*b*-PVBT/A-PEO supramolecular complex in DMF (*N,N*-dimethylformamide) common solvent and then added two different selective solvents of water and MeCN. By varying the molecular weights of the PS-*b*-PVBT block segments and the contents of the selective solvents, we obtained a variety of multi-compartment micelles: raspberry-like spheres, core-shell-corona spheres, core-shell-corona cylinders, nanostructured vesicles, onion structures, segmented worm-like cylinders, and woodlouse-like structures. Through simple blending of the A-PEO homopolymer and the PS-*b*-PVBT block copolymers, we could observe multi-compartment micelle structures similar to those formed by ABC miktoarm star terpolymers.

Experimental

Materials

Styrene and 4-vinylbenzyl chloride (VBC) are obtained from Aldrich, passed through an alumina column and then vacuum-distilled from CaH₂ under reduced pressure prior to use. TEMPO-OH initiator was synthesized as described previously.²⁹ PS-*b*-PVBT copolymers with different lengths of their chains containing T units were synthesized through nitroxide-mediated radical polymerization to yield PS-*b*-PVB_N₃, followed by click chemistry with PT.^{30–32} A-PEO was synthesized through the reaction of monomethoxy-poly(ethylene poly(ethylene oxide) with TsCl (to form PEO-TsCl) and a subsequent reaction with adenine and K₂CO₃ in DMF, as described previously.³³

Micelle structures from PS-*b*-PVBT/A-PEO supramolecular complexes

A PS-*b*-PVBT/A-PEO supramolecular complex was dissolved in DMF (5 mg mL⁻¹), which is a good solvent for all of the segments (PS, PVBT, and A-PEO). A volume of H₂O or MeCN was added gradually into the DMF solution of the blend, with stirring (H₂O and MeCN are non-solvents for the PS blocks). The formation of micelles was determined by the appearance of turbidity in the solution. The addition of H₂O or MeCN was continued until the desired concentration was reached; the DMF was then removed through dialysis against toluene.

Characterization

¹H and ¹³C NMR spectra were measured by using a Varian Unity Inova 500 spectrometer from solutions in CDCl₃ and *d*₆-DMSO. Molecular weights and polydispersity (PDI) were determined by using gel permeation chromatography (GPC) at

80 °C with a 410 differential refractometer, and three Ultrastay-gel columns (100, 500, and 103 Å) connected in series; DMF was the eluent; the flow rate was 1 mL min⁻¹. PS standards was used for the molecular weight calibration curve. The hydrodynamic diameters of the micelles were measured using Brookhaven 90Plus apparatus (Brookhaven Instruments, USA) for dynamic light scattering (DLS) at 25 °C and a He-Ne laser (power: 35 mW; wavelength: 632.8 nm) at an angle of detection of 90°. All samples were measured more than five times. Small-angle X-ray scattering (SAXS) analyses were recorded by using the BL17A1 wiggler beamline of the National Synchrotron Radiation Research Center (NSRRC), Taiwan. An X-ray beam having a diameter of 0.5 mm and a wavelength (λ) of 1.1273 Å⁻¹ was used for the SAXS measurements. Wide-angle X-ray diffraction (WAXD) data were determined using a NANOSTAR U X-ray scattering system (Bruker AXS, Karlsruhe, Germany) and Cu K α radiation (30 W, 50 kV, 600 μ A). Transmission electron microscopy (TEM) was performed using a JEOL 2100 microscope (Japan) operated at 200 kV. To observe the micelle structures under TEM and to maintain the same morphology as in the solution, a small amount of excess water solution was quenched to quickly vitrify the PS and PVBT blocks into their glass state and then the micelles were placed onto Cu grids, which were coated with carbon-supporting films. The micelles were observed by staining with I₂ vapor through exposure to determine the PVBT/A-PEO complexes since I₂ is a preferential staining agent for thymine (T) and adenine (A) units and thus, the domains of the PVBT/A complex appeared dark, and the domains of PS and PEO appeared bright in the TEM images.

Results and discussion

Self-assembly of PS-*b*-PVBT diblock copolymers in the bulk state

Table 1 summarizes the thermal properties and molecular weights, as determined through GPC (Fig. S1†), ¹H NMR spectroscopy (Fig. S2†), and DSC analyses, of the two PS-*b*-PVBT diblock copolymers used in this study. Fig. S3(a) and (b)† display the SAXS analysis data for pure PS₆₇-*b*-PVBT₁₆ and PS₈₇-*b*-PVBT₂₂. These two pure diblock copolymers possessed long-range-ordered lamellar microdomain structures, due to the high-order scattering peaks at the scattering vectors q ($q/q_m = 1, 2, 3, 4, \text{ and } 5$) relative to the first order scattering

Table 1 Molecular weights and thermal properties of PS-*b*-PVBT diblock copolymers used in this study

Sample ^a	PS (M_n) ^a	PVBT (M_n) ^a	PDI ^b	T_g (°C) ^c
PS ₆₇ - <i>b</i> -PVBT ₁₆	7100	8840	1.17	104/157
PS ₈₇ - <i>b</i> -PVBT ₂₂	9000	7400	1.20	109/165

^a Determined from ¹H NMR spectra. ^b Determined from GPC analysis. ^c Determined from DSC analysis.

peaks. TEM images [Fig. S3(c) and (d)†] confirmed these structures. The two SAXS peaks appearing at positions of multiple q of 0.041 and 0.025 \AA^{-1} indicate lamellar phases having long periods of 15.3 and 25.1 nm based on the first peak position ($2\pi/q$), for pure PS₆₇-*b*-PVBT₁₆ and PS₈₇-*b*-PVBT₂₂, respectively. The result is reasonable: the pure PS₈₇-*b*-PVBT₂₂ diblock copolymer should exhibit larger alternating lamellar domains in the bulk state because its molecular weight is higher than that of PS₆₇-*b*-PVBT₁₆, while their volume fractions of PS blocks are similar ($f_{\text{ps}}^v = 0.64$).³⁰

Self-assembly of PS-*b*-PVBT/A-PEO supramolecular complexes in DMF/H₂O solution

Pure PS-*b*-PVBT diblock copolymers are not able to self-assemble in the selective solvent of a water solution because both blocks are hydrophobic. In contrast, the A-PEO homopolymer is water-soluble and hydrophilic; therefore, we expected the supramolecular complex of PS-*b*-PVBT/A-PEO to be able to form self-assembled micelles in the water selective solvent.

The self-assembled structures from spherical micelles to cylinders, vesicles, and lamellae can be mediated by changing the amounts of selective solvent to shift the micro-phase separation of the block copolymers.^{34,35} We first dissolved a PS-*b*-PVBT/A-PEO supramolecular complex in DMF common solvent, which is a good solvent for PS, PVBT and A-PEO segments. Then, we added the selective solvent of water or MeCN, a poor solvent for PS and PVBT blocks, very slowly. Cheng *et al.* have reported the micellization and the morphological transition of the PS-*b*-PEO block copolymer in both DMF/H₂O and DMF/MeCN systems, which was strongly dependent on the water and MeCN contents in these studies.^{36,37} As a result, we also chose these two different selective solvents of H₂O and MeCN to investigate their self-assembly effects on our PS-*b*-PVBT/A-PEO supramolecular complexes in this study.

Fig. 1 presents TEM images of a PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex where the T/A ratio was 1 : 1 in DMF/H₂O solutions containing various H₂O ratios. We observed a raspberry-like sphere (or sphere-on-sphere) structure [Fig. 1(a)]

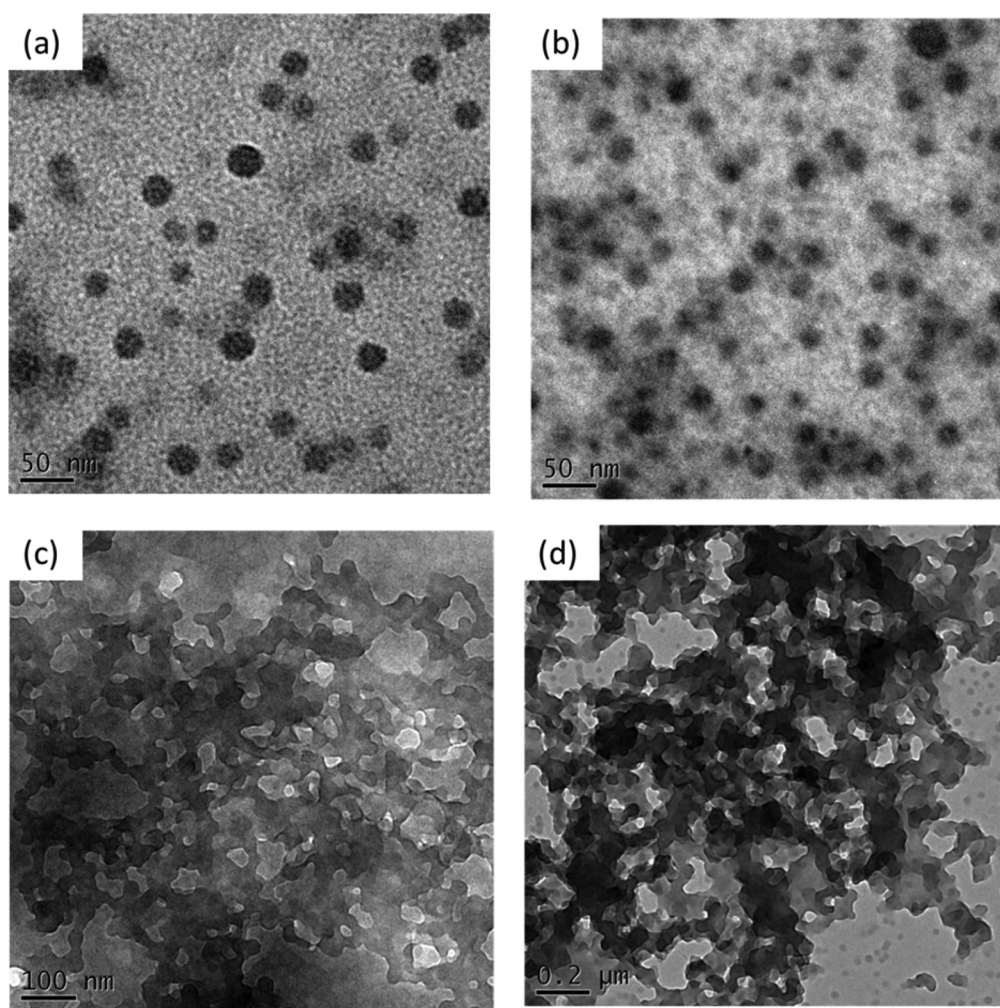


Fig. 1 TEM images of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in DMF/H₂O solutions containing various water contents of (a) 1, (b) 2, (c) 5, and (d) 10 wt%.

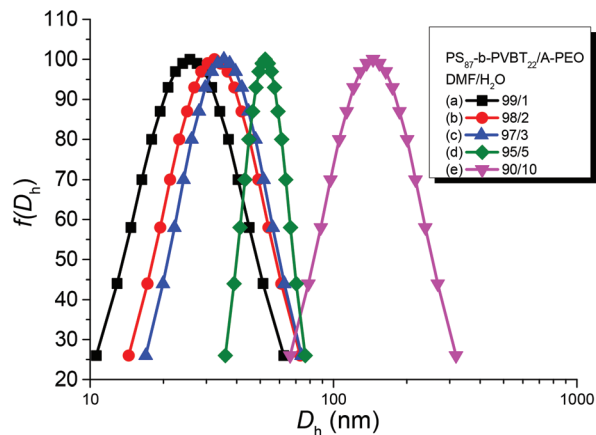


Fig. 3 DLS data for the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in DMF/H₂O solutions at various water contents of (a) 1, (b) 2, (c) 3, (d) 5, and (e) 10 wt%.

at a relatively low concentration of water (1 wt%). Diblock copolymers always show spherical micelles having a hydrophobic core and a hydrophilic shell after the addition of water.³⁸ In this study, the hydrophilic A-PEO coronas imparted solubility to the spherical micelles in water, while their hydrophobic PS and PVBT block segments should be thermodynamically immiscible (Fig. S3†), resulting in strong microphase separation in the bulk state. Therefore, we observed raspberry-like (“sphere-on-sphere”) spheres with nearly identical sizes (*ca.* 20–30 nm) for the multi-compartment micelles in Fig. 2(a) and (b), as confirmed through DLS [Fig. 2(e)]. This raspberry-like sphere is close to the diameter of the full contour length of the chain. A schematic representation of the possible morphology is displayed in Fig. 2(c), with the interface between PVBT and A-PEO connected through T and A multiple hydrogen bonding interactions [Fig. 2(d)]. Fig. 1(b) reveals that spherical micelle morphologies also formed at a 2 wt% water concentration. At concentrations of 5 and 10 wt%, however, the morphologies changed to long, wormlike cylinders [several micrometers; Fig. 1(c) and (d)]. Because of the immiscibility of the PS and PVBT block segments, these wormlike structures may have possessed core-shell-corona cylinder structures, as displayed in Fig. 2(f) and (g). Fig. 3 summarizes the hydrodynamic diameters through DLS data of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in the DMF/water system. The addition of 1 wt% water led to polymer aggregate sizes *ca.* 20–30 nm; this range is consistent with the TEM images. Further increasing the water content to 2 or 3 wt% caused the sizes of micelles to increase accordingly, as expected. At 5 or 10 wt% water content, cylindrical structures were formed, resulting in values of D_h larger than those of the spherical structures.

To observe the structures formed at water contents higher than 10 wt%, we examined the PS₆₇-*b*-PVBT₁₆/A-PEO supramolecular complex in the DMF/water system; the lower molecular weight of the PS block decreased the core-chain

stretching and inhibited precipitation in the DMF/water system at elevated water contents. Fig. 4 presents TEM images of the PS₆₇-*b*-PVBT₁₆/A-PEO supramolecular complexes formed at a T/A ratio of 1 : 1 in DMF/H₂O solutions with various water ratios. Vesicle structures were clearly observed for all of the high-water-content systems (>10 wt%). As revealed in Fig. 4(a)–(d), vesicles with bilayer structures were formed; Fig. 5(a) displays an enlarged image. Almost monodisperse bilayer vesicles were evident at 10 and 15 wt% water contents, with the sizes of the vesicle micelles determined from the TEM images, which are close to the hydrodynamic diameters based on the DLS data [*ca.* 150–200 nm; Fig. 5(c)]. Vesicle structures can form readily with low bilayer bending elasticity and high surface tension as revealed in Fig. 5(b) and (e). When the water content was 10 or 15 wt%, the conformations of the PS and PVBT blocks were extended relative to those at water contents below 10 wt%, allowing the block copolymer chains to pack in parallel to micelles having layered lamellae structures. Ultimately, the structures formed vesicles to minimize the surface energy in solution. We suspect that the inner- and outer-layer polymer chains of the vesicles were located on the A-PEO homopolymer segment, as displayed in Fig. 5(b). PS and PVBT block segments are immiscible, and PVBT can undergo complementary multiple hydrogen bonding with A-PEO. Therefore, the resulting vesicular complex is composed of an outer layer of PEO segments (majority), a trilayer of a PVBT/PS/PVBT microphase-separated wall (*ca.* 30 nm, double size of lamellar thickness based on SAXS analyses in Fig. S3†), and an inner layer of PEO segments (majority). Further increasing the water content to 25 or 35 wt% also led to the observation of vesicle micelles, as revealed in Fig. 4(e)–(g). The vesicles were formed among in-plane bilayer structures;^{4,39} Fig. 5(d) displays an expanded image. The sizes of the vesicle micelles increased to 200–250 nm compared with relatively low water contents (10–15 wt%) as shown by DLS data in Fig. 5(f). Here, the wall thickness of the vesicle is *ca.* 30 nm, which is close to that found in a previous study of the vesicle structure of PS-*b*-PEO diblock copolymers in a DMF/H₂O system.³⁶ With further increase of the water content, the PS chain mobility in the core decreased and the PS and PVBT block segments underwent multi-layer microphase separation, as presented in Fig. 5(e), to further minimize the free energy. Thus, water-insoluble and hydrophobic PS-*b*-PVBT diblock copolymers can readily undergo self-assembly to form multi-compartment micelles upon simple blending with a water-soluble A-PEO homopolymer, stabilized by multiple hydrogen bonding interactions between the PVBT and A-PEO block segments, in DMF/H₂O solution.

Self-assembly of micellar structures from PS-*b*-PVBT/A-PEO supramolecular complexes in DMF/MeCN solution

Fig. 6 presents TEM images of the PS₆₇-*b*-PVBT₁₆/A-PEO supramolecular complexes formed at a T/A ratio of 1 : 1 in DMF/MeCN solution at various MeCN contents. Only spherical micelles were formed, regardless of the MeCN concentration. These spheres had sizes of approximately 100–200 nm at

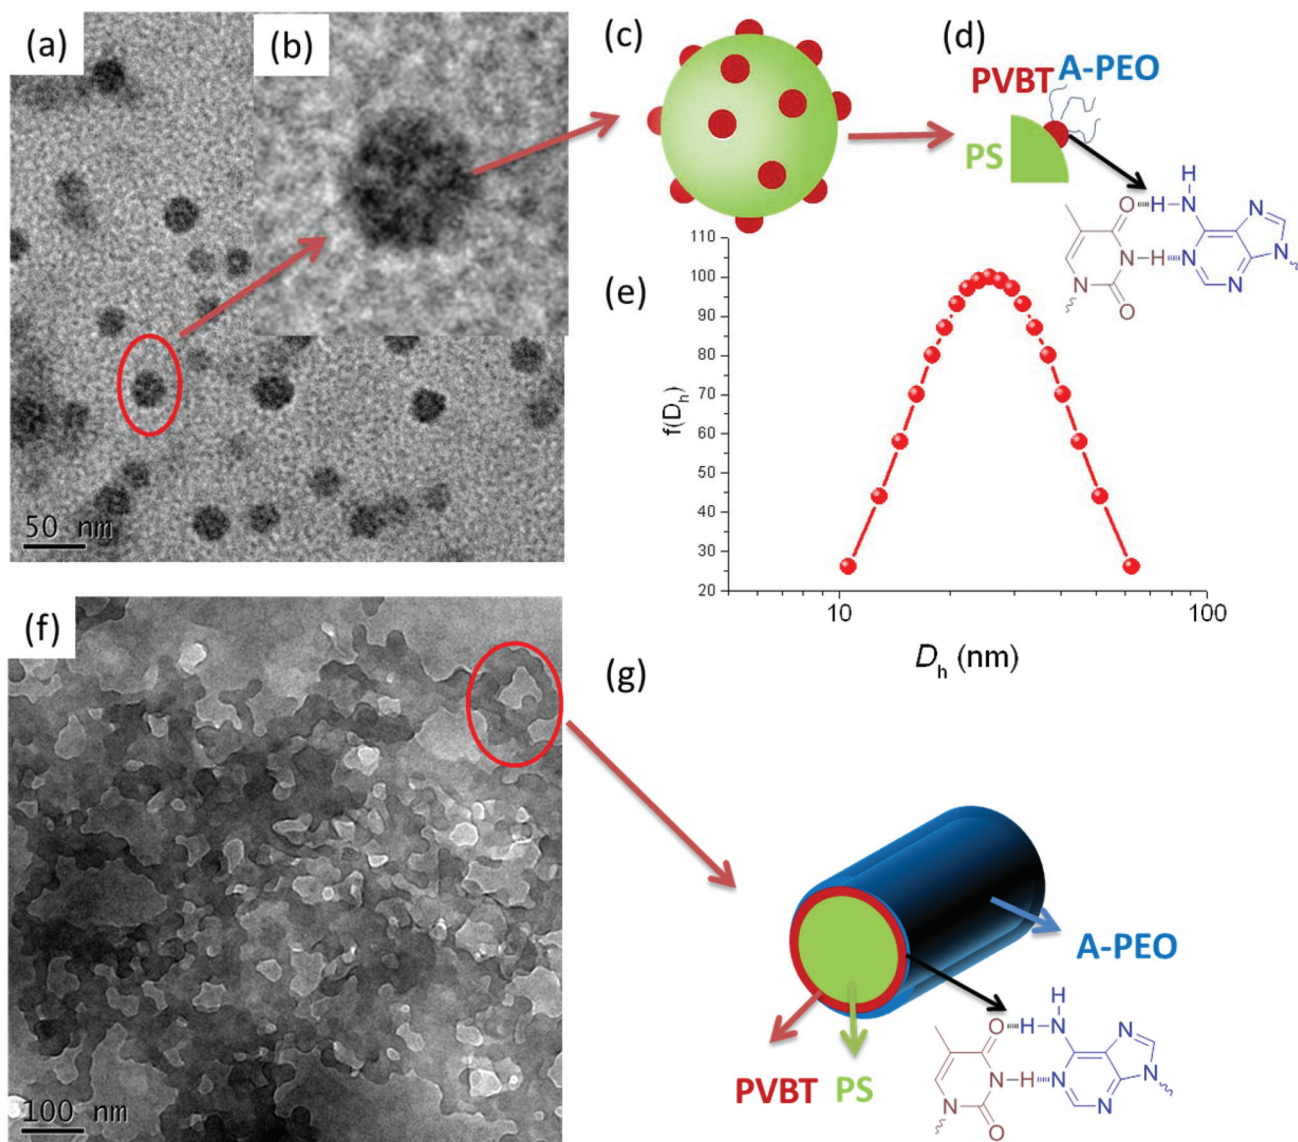


Fig. 2 (a) TEM image of PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex formed in DMF/H₂O solution at 1 wt% water content. Inset (b): Magnified image of (a). (c–d) Schematic representation of the raspberry-like spheres in (a). (e) Size-distribution of the micelles by DLS. (f) TEM image of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex formed in DMF/H₂O solution at 5 wt% water content. (g) Schematic representation of a possible structure for the core–shell–corona cylinder morphology observed in the TEM image in (f).

MeCN contents of 10 and 30 wt%, which is consistent with the DLS data in Fig. 6(f) (black line). Further increasing the MeCN content to 50 wt% resulted in spheres of near-uniform size (*ca.* 400–500 nm), as confirmed from the DLS data in Fig. 6(f) (red line). These spherical nanoparticles possess uniform size (*ca.* 150–200 nm) at the highest MeCN content (70 wt%), as confirmed from the DLS data in Fig. 6(f) (blue line). The sizes determined from the TEM images were generally smaller than DLS measurements because TEM sample preparation generally unavoidably led to chain-collapse and micelle-shrinkage during evaporation of the micelle particles. The different morphological transitions of the PS₆₇-*b*-PVBT₁₆/A-PEO supramolecular complexes in the DMF/H₂O and DMF/MeCN systems

were because of the different PS-solvent interaction parameters (χ). H₂O is a much poorer solvent than MeCN for PS segments since the $\chi_{\text{PS-water}}$ value is *ca.* nine times higher than the value of $\chi_{\text{PS-MeCN}}$.^{36,37} The interfacial free energy increase is able to increase the micelle size and then increase the stretching of the PS blocks in the cores, resulting in the spheres readily changing to form cylinders in the DMF/H₂O system to minimize the free energy. This morphological change was not observed for the PS₆₇-*b*-PVBT₁₆/A-PEO supramolecular complexes in the DMF/MeCN system because of the relatively low value of $\chi_{\text{PS-MeCN}}$. The larger selective solvent content is necessary to change the interfacial free energy at a certain critical point; however, in this study we could not determine this

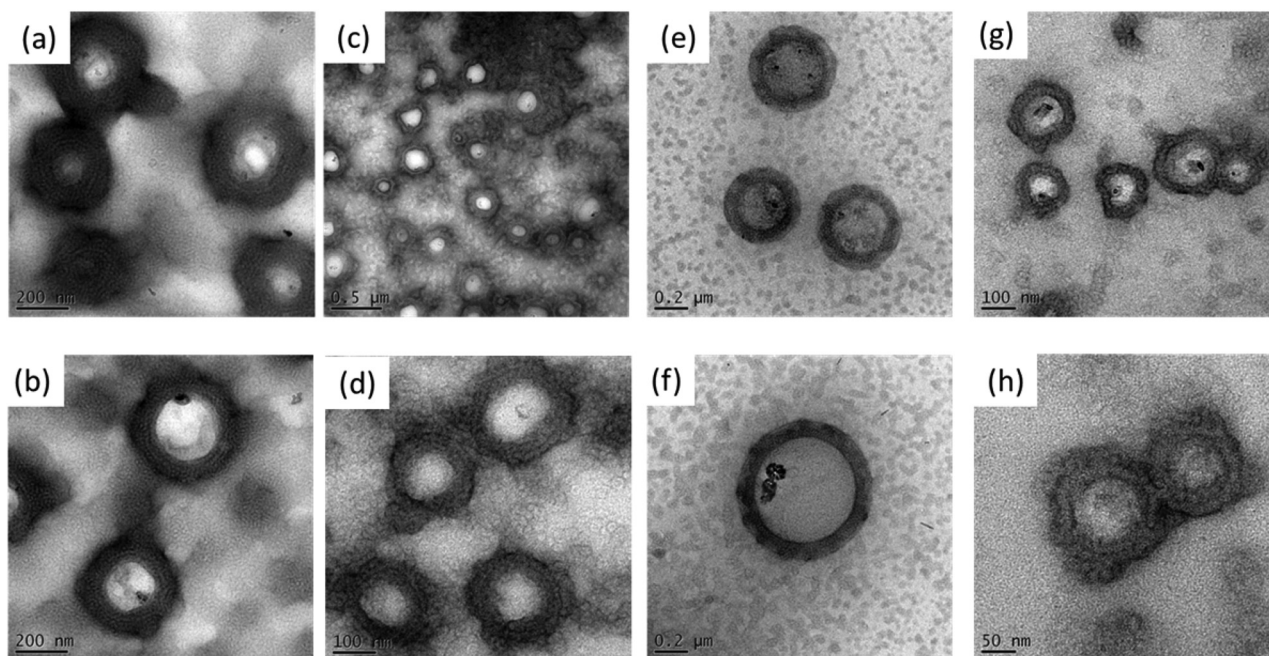


Fig. 4 TEM images of the PS_{67} - b - $PVBT_{16}$ /A-PEO supramolecular complexes formed in DMF/ H_2O solutions at various water contents of (a and b) 10, (c and d) 15, (e and f) 25, and (g and h) 35 wt%.

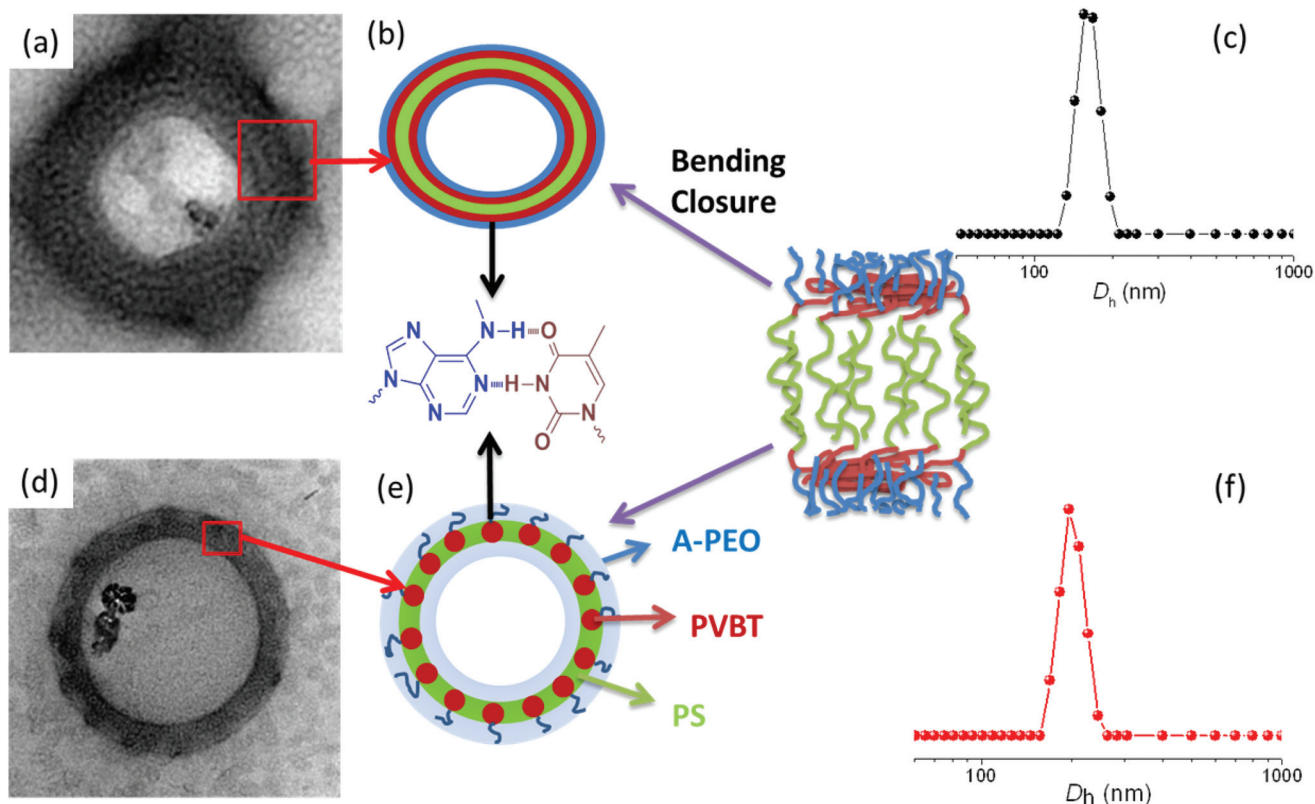


Fig. 5 (a) Expanded TEM images of the PS_{67} - b - $PVBT_{16}$ /A-PEO supramolecular complex formed in DMF/ H_2O solution at 10 wt% water content. (b) Schematic representation of the possible layer-vesicle structure observed in the TEM image in (a). (c) Size-distribution of the micelles by using DLS. (d) TEM image of the PS_{67} - b - $PVBT_{16}$ /A-PEO supramolecular complex formed in DMF/ H_2O solution at 25 wt% water content. (e) Schematic representation of the possible in-plane layer vesicle structure observed in (d). (f) Size-distribution of the micelles by using DLS, corresponding to the TEM image in (d).

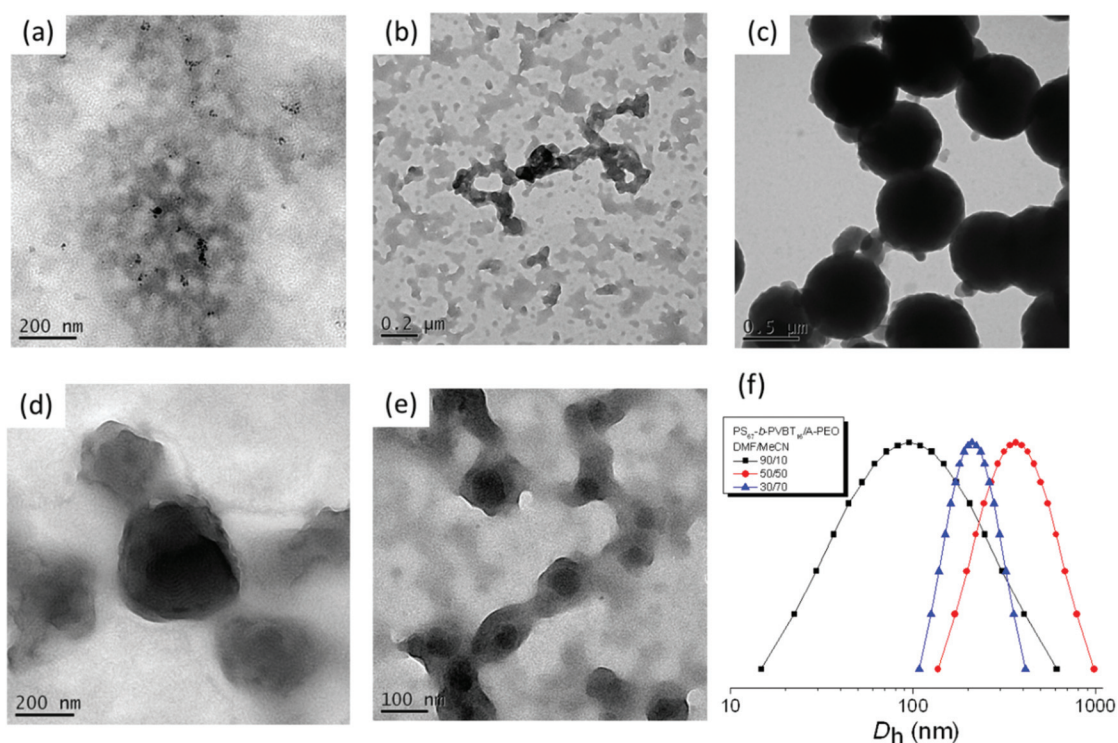


Fig. 6 (a–e) TEM images of the $\text{PS}_{67}\text{-}b\text{-PVBT}_{16}/\text{A-PEO}$ supramolecular complexes formed in DMF/MeCN solution at various MeCN contents of (a) 10, (b) 30, (c) 40, (d) 50, and (e) 70 wt%. (f) Corresponding size-distributions of the micelles by using DLS.

value, even at 70 wt% MeCN content.⁴⁰ To observe the morphological change in the DMF/MeCN system, we turned to the $\text{PS}_{87}\text{-}b\text{-PVBT}_{22}/\text{A-PEO}$ supramolecular complex in the DMF/MeCN system because the higher molecular weight of the PS block would presumably increase the core-chain stretching and the interfacial tension between the solvent and the micellar core. As a result, we anticipated the possibility of observing a morphological change in the DMF/MeCN system.

Fig. 7 displays TEM images of the $\text{PS}_{87}\text{-}b\text{-PVBT}_{22}/\text{A-PEO}$ supramolecular complexes formed when the T/A ratio was 1 : 1 in DMF/MeCN solutions at various MeCN contents. Fig. 7(a)–(c) reveal clear core–shell–corona spherical micelles at a MeCN content of 10 wt%; Fig. 8(a) and (b) present expanded images. The sizes of these core–shell–corona spherical micelles, determined from the TEM images, were approximately 20–40 nm, consistent with the values from the DLS data in Fig. 8(d). From the combination of TEM images in Fig. 8(a) and (b), all of the core–shell–corona spherical micelles featured dense dark cores (PS majority), surrounded by less-dense shells (PVBT majority), and a relatively clear boundary; the black ring in Fig. 8(a) arises from the presence of complementary T...A multiple hydrogen bonds in the PVBT/A-PEO complex, because I_2 will stain the A units, as displayed in Fig. 8(c). Further increasing the MeCN content to 30 wt%, we observed clear cylinder structures [Fig. 7(d)–(f)] and, thus, values of D_h larger than those for the spherical structure in Fig. 8(g). These wormlike structures may be similar to those formed in the DMF/H₂O system,

with a core–shell–corona cylinder structure, as presented in Fig. 8(f). The structure of the $\text{PS}_{87}\text{-}b\text{-PVBT}_{22}/\text{A-PEO}$ supramolecular complex was quite different from that of the $\text{PS}_{67}\text{-}b\text{-PVBT}_{22}/\text{A-PEO}$ supramolecular complex at a MeCN content of 30 wt%. The higher molecular weight of the PS block would increase the core-chain stretching and the interfacial tension between the solvent and the micellar core; thus, the spheres would change to cylinder structures at the same MeCN content to minimize the free energy as a result of decreasing the stretching penalty of the PS chains. More interestingly, upon increasing the MeCN content further, to 70 wt%, we observed regular multi-lamellar spherical structures (onion structures) and segmented worm-like structures (woodlouse structures) in Fig. 7(g)–(i). These spherical and segmented worm-like structures had sizes mostly in the range 150–300 nm, as confirmed by the DLS data in Fig. 9(f). These onion-like spheres were in the form of compact multi-lamellar vesicular structures.^{41–43} Onion-like microspheres have received much attention due to their potential application as carriers for controlled-release systems;⁴⁴ onion-like morphologies have been reported widely in the bulk state, formed from triblock copolymers, copolymer/homopolymer blends, and copolymer/copolymer blends, where thermodynamic equilibrium plays an important role.^{45,46} In this study, we observed onion structures of various sizes and with different numbers of ring patterns [Fig. 9(a)]. As revealed in Fig. 4, the vesicle structure arose from the bilayer structure of the supramolecular complex of (PEO-A/PVBT-*b*-PS/

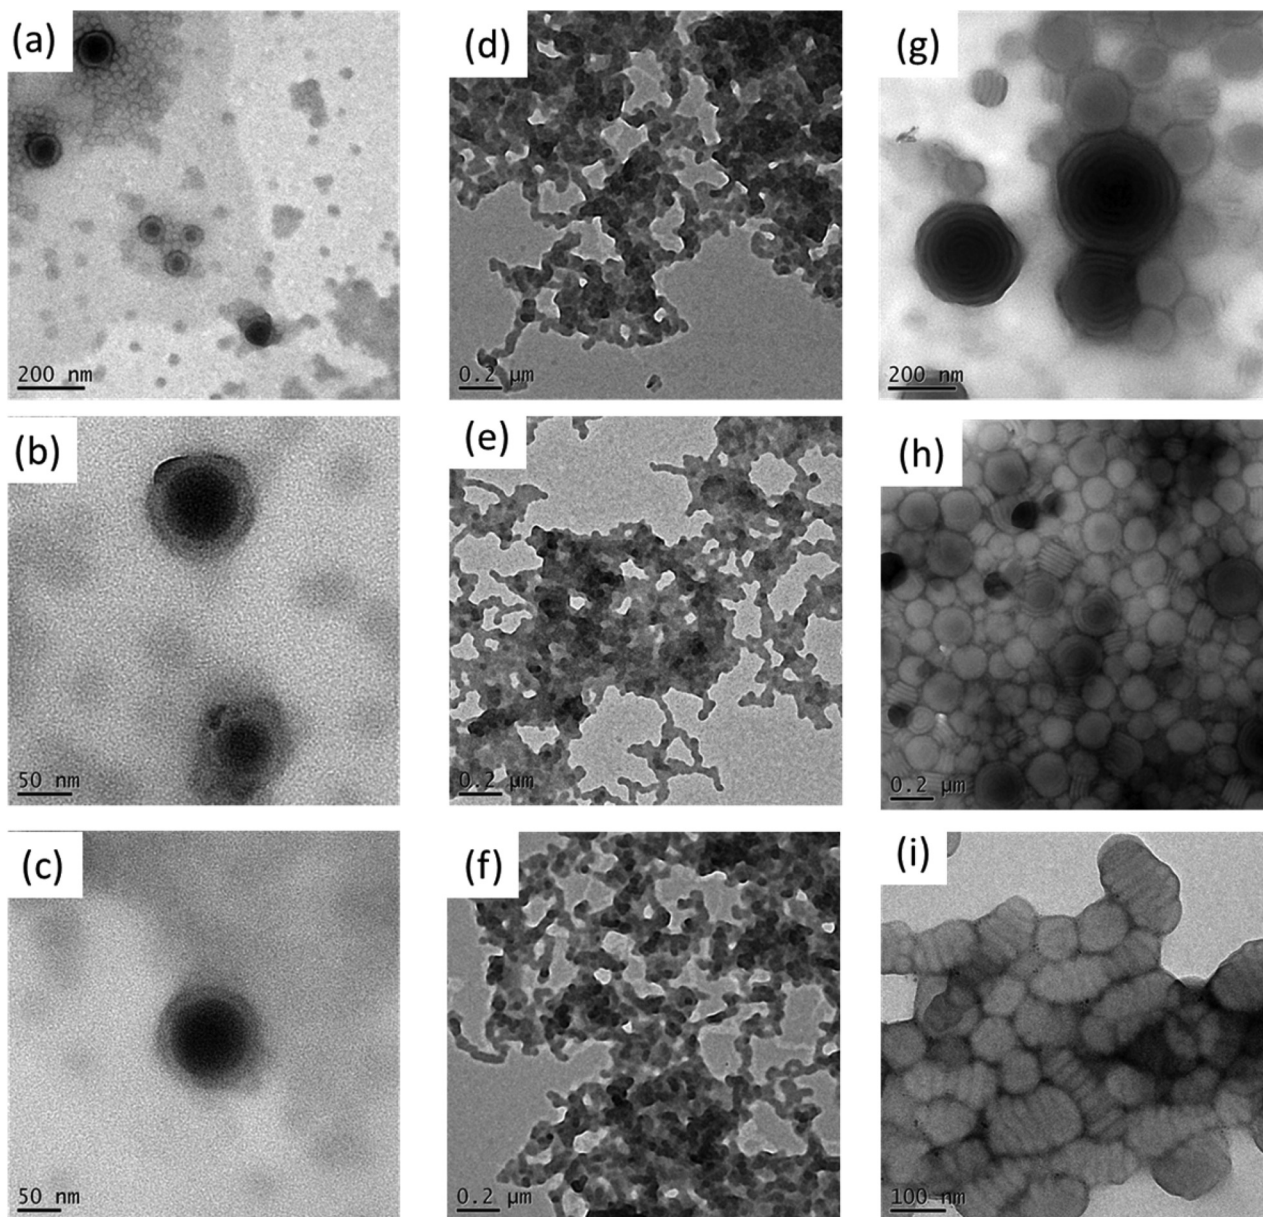


Fig. 7 TEM images of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in DMF/MeCN solution at various MeCN contents of (a–c) 10, (d–f) 30, and (g–i) 70 wt%.

PS-*b*-PVBT/A-PEO). At a high MeCN content (70 wt%), the micelle structure was close to precipitating and close to behaving as in the bulk state. Therefore, the double-bilayer structure of (PEO-A/PVBT-*b*-PS/PS-*b*-PVBT/A-PEO) bent into relatively smaller onion structures, with no MeCN existing inside the micelle structure because the relatively low interaction parameter ($\chi_{\text{PS-MeCN}}$) did not induce strong segregation between the PS block and the MeCN solvent; the triple bilayer structure of (PEO-A/PVBT-*b*-PS/PS-*b*-PVBT/A-PEO) also bent into relatively larger onion structures [Fig. 9(b) and (c)]. From these results, we may suspect that these onion structures in this system may have possessed non-equilibrium or kinetically captured morphologies, because the PS and PVBT block segments [with rela-

tively high glass transition temperatures (T_g)] were in the glassy state, with their mobilities decreasing significantly, at this higher MeCN content. Muller *et al.* reported that the poly (butadiene-*b*-*tert*-butyl methacrylate-*b*-*N*-methyl-2-vinylpyridinium) (PB-*b*-PtBMA-*b*-P2VPq) ABC miktoarm star terpolymer forms a segmented worm-like structure (woodlouse structure); they also observed an onion structure.¹⁴ In our present study, we observed almost the same woodlouse structures at higher MeCN content. We propose that these woodlouse structures [Fig. 9(d) and (e)] may have arisen from further microphase separation of the onion structure. To confirm this phenomenon, we controlled the graft density of the A-PEO segment on the PS-*b*-PVBT block segments. The advantage of preparing

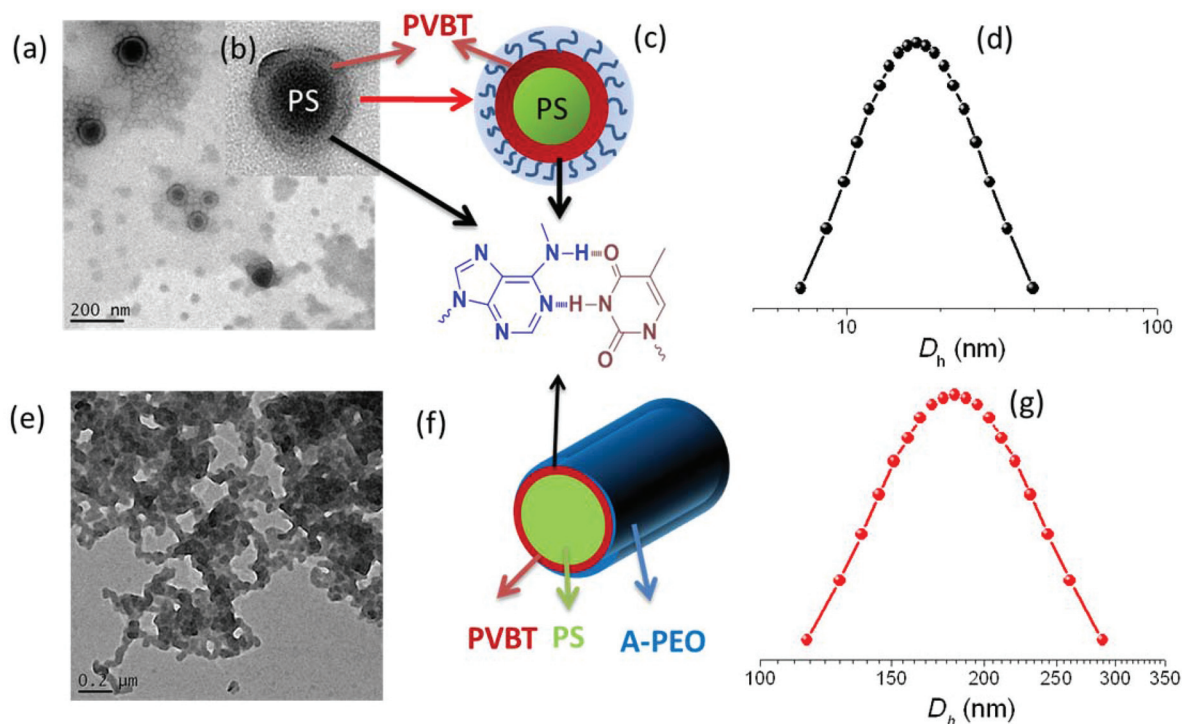


Fig. 8 (a and b) Expanded TEM images of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex formed in DMF/MeCN solution at a MeCN content of 10 wt%. (c) Schematic representation of the possible core-shell-corona sphere morphology observed in the TEM image in (b). (d) Size-distribution of the micelle corresponding to the TEM image in (a) by using DLS. (e) TEM image of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex formed in DMF/MeCN solution at a MeCN content of 30 wt%. (f) Schematic representation of the possible core-shell-corona cylinder morphology observed in the TEM image in (e). (g) Size-distribution of the micelles by using DLS, corresponding to the TEM image in (e).

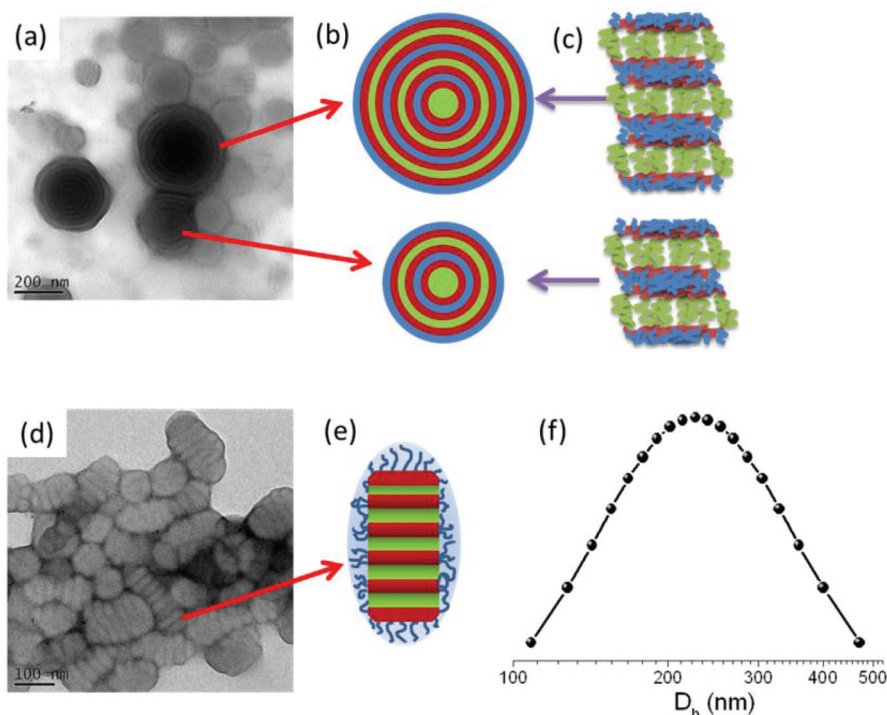


Fig. 9 (a and d) TEM images of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complex in DMF/MeCN solution at a MeCN content of 70 wt%. (b and c) Schematic representation of the possible onion sphere structure observed in the TEM image in (a). (e) Schematic representation of the possible wood-louse structure observed in the TEM image in (d). (f) Size-distribution of the micelles by using DLS, corresponding to the TEM images in (a) and (d).

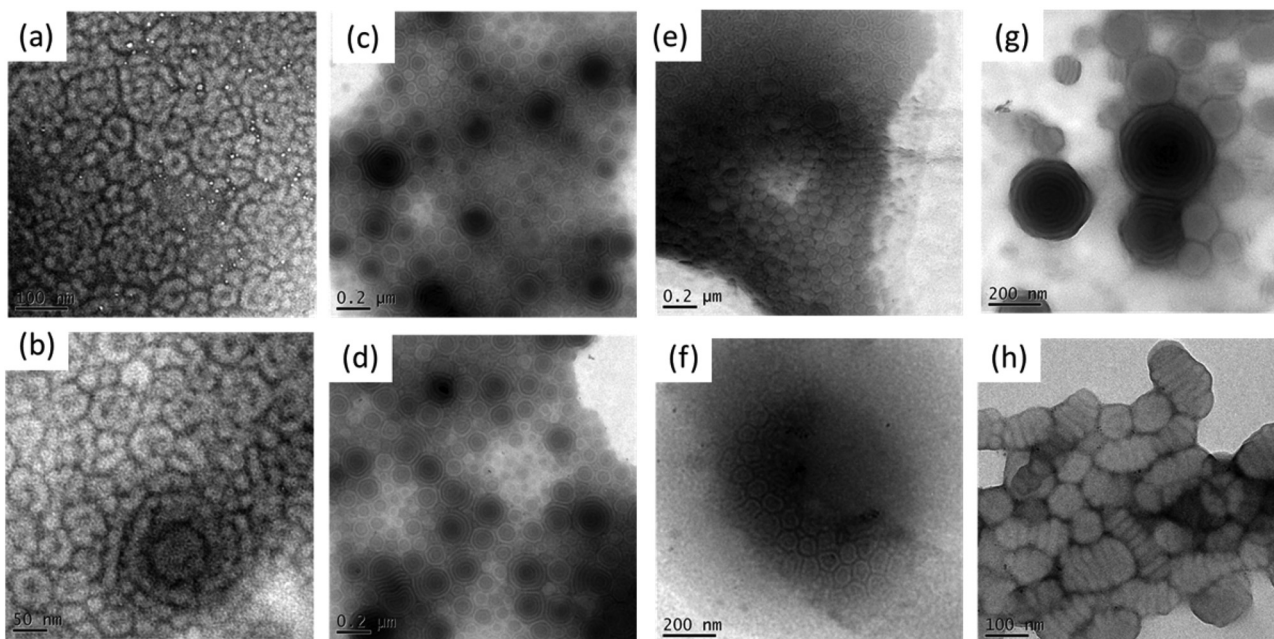


Fig. 10 TEM images of PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in DMF/MeCN solution at a MeCN content of 70 wt% at T/A ratios of (a and b) 1 : 0.3, (c and d) 1 : 0.5, (e and f) 1 : 0.7, and (g and h) 1 : 1.

pseudo *A-b-(B-g-C)* terpolymers from this PS-*b*-PVBT/A-PEO supramolecular complex is that we could readily control the grafting density of PEO by blending with different ratios of A-PEO homopolymer—much easier than having to synthesize individual covalently linked *A-b-B-g-C* terpolymers.

Fig. 10 presents TEM images of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed at various T/A ratios in DMF/MeCN solution at a MeCN content of 70 wt%. We observed short-range-ordered worm-like and spherical structures at a T/A ratio of 1 : 0.3, as revealed in Fig. 10(a) and (b), presumably because the relatively low A-PEO content did not provide a sufficiently large outer layer to protect the PS-*b*-PVBT block segments from precipitation while it was difficult to self-assemble them into a regular micelle structure. In contrast, increasing the T/A ratio to 1 : 0.5 [Fig. 10(c) and (d)] or 1 : 0.7 [Fig. 10(e) and (f)], we observed almost-onion structures; thus, increasing the PEO grafting density stabilized and enhanced the regular multi-compartment micelle structures. Similar to the structures in Fig. 7(g)–(i), we observed regular woodlouse structures in Fig. 10(g) and (h) when the T/A ratio was 1 : 1. In addition, the sizes of micelles increased upon increasing the T/A ratio, as revealed in Figs. 10 and 11. Furthermore, the PDI of the values of D_h also increased upon increasing the T/A ratio, because the segmented worm-like structure (woodlouse structure) would increase the PDI of the values of D_h relative to that of the spherical onion structure. More interestingly, we observed an intermediate structure between the onion structure and the woodlouse structure in Fig. 12(a) for a T/A ratio of 1 : 0.5, a segmented woodlouse structure existing between two onion structures. Further increasing the T/A ratio to 1 : 1, we

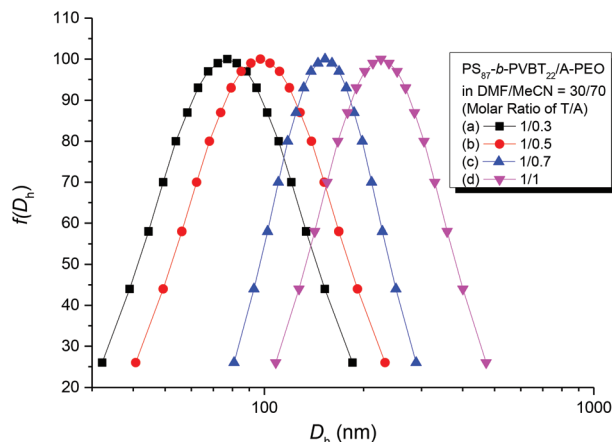


Fig. 11 DLS data of PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed in DMF/MeCN solution at a MeCN content of 70 wt% at T/A ratios of (a) 1 : 0.3, (b) 1 : 0.5, (c) 1 : 0.7, and (d) 1 : 1.

found almost the same segmented woodlouse structure as that in Fig. 12(b). Therefore, increasing the A-PEO grafting density to equal stoichiometry with PVBT led to equilibrium between the segmented worm-like or woodlouse structures in this study.

WAXD analyses of PS-*b*-PVBT/A-PEO supramolecular complexes

To realize the phase separation and crystallization behavior of the A-PEO segments in the different selective solvents, we pre-

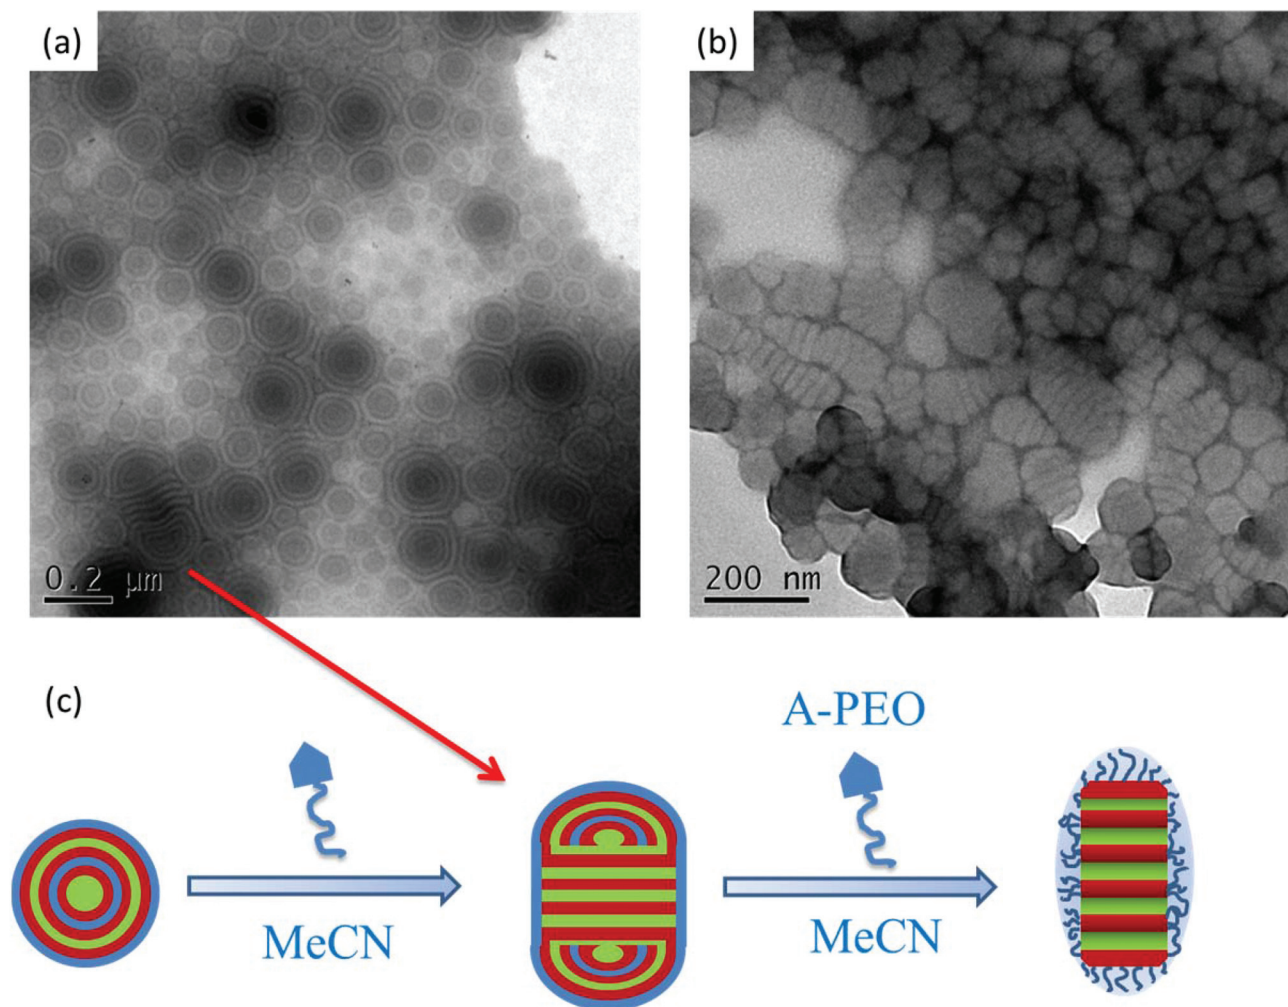


Fig. 12 TEM images of PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes formed at T/A ratios of (a) 1:0.5 and (b) 1:1. (c) Possible morphologies, from onion structures to woodlouse structures, formed in the DMF/MeCN solution at a MeCN content of 70 wt%.

pared thin films of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes through spin coating onto silicon wafers from DMF/H₂O and DMF/MeCN solutions. Fig. 13 displays the WAXD patterns of the PS₈₇-*b*-PVBT₂₂/A-PEO supramolecular complexes. No diffraction peaks were evident for the PS-*b*-PVBT block copolymer in Fig. 13(a), as would be expected for the amorphous segments of both the PS and PVBT blocks. For PS-*b*-PVBT/A-PEO mixtures dissolved in the common solvent DMF, we observed weak diffraction peaks in Fig. 13(b), indicating that the PEO segment could not crystallize by itself because of the high solubility of the PEO segment in the common solvent DMF. In contrast, the addition of a selective solvent, either water or MeCN, caused diffraction peaks to appear, with increased intensity upon increasing the content of the selective solvent [Fig. 13(A) for water; Fig. 13(B) for MeCN]. An obvious diffraction peak corresponding to the (120) plane of the PEO crystallite at a value of 2θ of 19.1° appeared in the WAXD patterns upon increasing the content of each selective solvent; a similar result has been observed for a pure

A-PEO homopolymer.⁴⁷ As a result, the addition of a selective solvent into a solution of the PS-*b*-PVBT/A-PEO supramolecular complex could enhance the microphase separation of the A-PEO and PS-*b*-PVBT block copolymer segments, thereby inducing micelle structures in solution. The most important feature was multiple hydrogen bonding between the T groups of PVBT and the A group of A-PEO. We recorded ¹H NMR spectra of PT (as a model compound for PVBT) and A-PEO to confirm the presence of multiple hydrogen bonding interactions between the T groups of PVBT and the A group of A-PEO (Fig. S4†). The addition of A-PEO to a solution of PT led to a downfield shift of the signal for the NH unit of the T group, appearing initially at 8.40 ppm and moving to 10.38 ppm when the T/A ratio was 1:1.^{48,49} Similarly, the addition of PT to a solution of A-PEO resulted in a downfield shift of the signal of the NH₂ unit of the A group, from 5.64 to 6.40 ppm, confirming that multiple intermolecular hydrogen bonding occurred between their T and A groups.


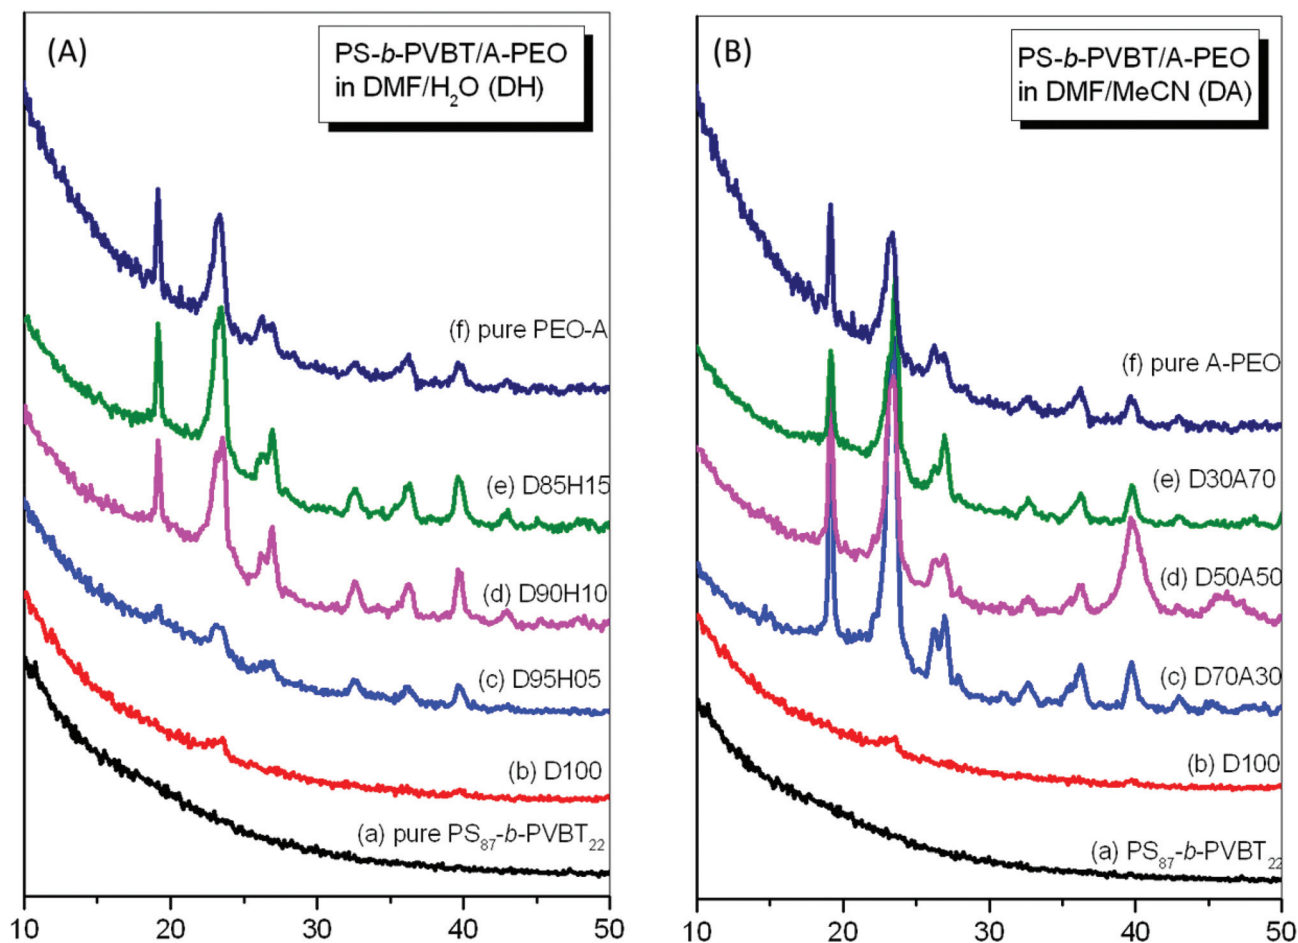


Fig. 13 WAXD patterns of $PS_{87}\text{-}b\text{-}PVBT_{22}/A\text{-}PEO$ supramolecular complexes formed at various contents of the selective solvent: (A) DMF/ H_2O and (B) DMF/MeCN solutions.

Scheme 2 summarizes the morphologies of the multi-compartment micelles obtained from the $PS\text{-}b\text{-}PVBT/A\text{-}PEO$ supramolecular complexes in this study. By varying the molecular weights of the $PS\text{-}b\text{-}PVBT$ block segments and increasing the content of water as the selective solvent, we could change the structures of the multi-compartment micelles from raspberry-like spheres to core-shell-corona cylinders to trilayer vesicles to in-plane multilayer vesicle structures [Scheme 2(a)–(d)]. Similarly, the multi-compartment micelles changed from core-shell-corona spheres to core-shell-coronal cylinders to onion-like structures to woodlouse structures upon increasing the content of MeCN [Scheme 2(e)–(h)]. Through simple blending of the A-PEO homopolymer into the $PS\text{-}b\text{-}PVBT$ block copolymers, we could also observe changes in the structures of the multi-compartment micelles that were similar to those of ABC miktoarm star terpolymers. A further attractive feature of this supramolecular complex is that we could readily control the grafting density of the PEO segment through simple blending with different amounts of the A-PEO homopolymer; in comparison, it is difficult to control the structures of real (*i.e.* covalent) $A\text{-}b\text{-}(B\text{-}g\text{-}C)$ terpolymers.

Conclusions

We have proposed a simple but effective method for preparing various multi-compartment micelle structures from $PS\text{-}b\text{-}PVBT/A\text{-}PEO$ supramolecular complexes, which undergo hierarchical self-assembly through the multiple hydrogen bonding interaction of their T and A units. We grafted A-PEO onto $PS\text{-}b\text{-}PVBT$ diblock copolymers to form pseudo $A\text{-}b\text{-}(B\text{-}g\text{-}C)$ terpolymers stabilized through complementary multiple hydrogen bonding in DMF solution; increasing the content of added water as a selective solvent transformed the morphology from raspberry-like spheres to core-shell-corona cylinders to trilayer vesicles to in-plane multilayer vesicles. Likewise, the morphologies of the multi-compartment micelles changed from core-shell-corona spheres to core-shell-coronal cylinders to onion structures to woodlouse structures upon increasing the MeCN content. We are optimistic that this simple method will facilitate the development of various other multi-compartment micelles for biomedical use as well as templates for the synthesis of unprecedented porous inorganic nanomaterials.

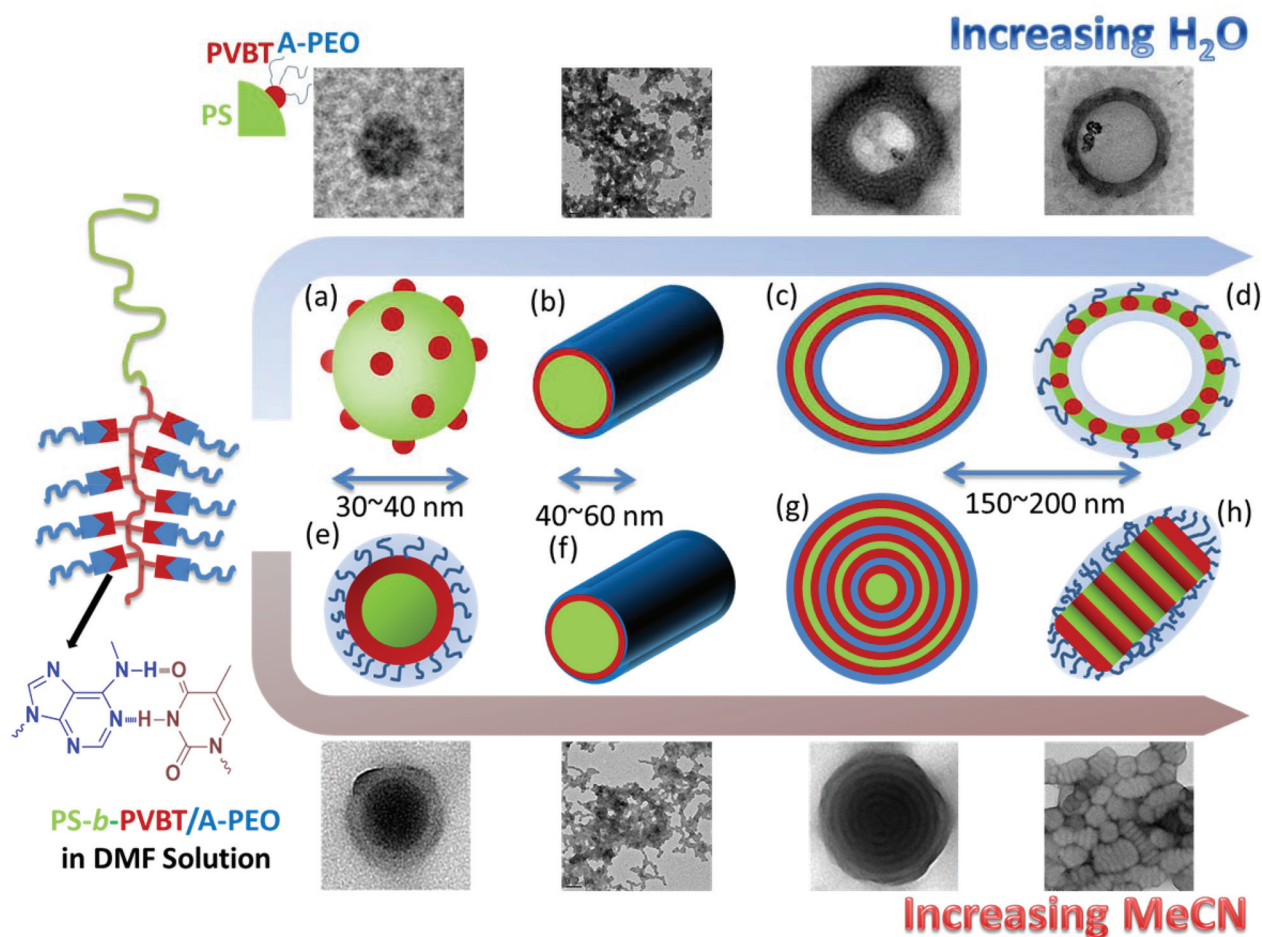

Scheme 2 Changes in the multi-compartment micelle structures of PS-*b*-PVBT/A-PEO supramolecular complexes in DMF solution upon increasing the contents of (a)–(d) H₂O and (e)–(h) MeCN as selective solvents.

Acknowledgements

This study was supported financially by the Ministry of Science and Technology, Republic of China, under contracts MOST 100-2221-E-110-029-MY3 and MOST 102-2221-E-110-008-MY3. Dr Yi-Chen Wu also thanks the 2014 New Partnership Program for the Connection to the Top Labs in the World under contracts MOST 103-2911-I-110-513 that helped initiate this study. We also thank Mr Hsien-Tsan Lin (Regional Instruments Center at National Sun Yat-Sen University) for his help with TEM experiments.

References

- 1 L. Zhang and A. Eisenberg, *J. Am. Chem. Soc.*, 1996, **118**, 3168–3181.
- 2 A. Halperin, M. Tirrell and T. P. Lodge, *Adv. Polym. Sci.*, 1992, **100**, 31–71.
- 3 G. Kaur, L. Y. Chang, T. D. M. Bell, T. W. Hearn and K. Saito, *J. Polym. Sci., Part A: Polym. Chem.*, 2011, **49**, 4121–4128.
- 4 A. O. Moughton, M. A. Hillmyer and T. P. Lodge, *Macromolecules*, 2012, **45**, 2–19.
- 5 S. Kubowicz, J. F. Baussard, J. F. Lutz, A. F. Thunemann, H. von Berlepsch and A. Laschewsky, *Angew. Chem., Int. Ed.*, 2005, **44**, 5262–5265.
- 6 H. von Berlepsch, C. Bottcher, K. Skrabania and A. Laschewsky, *Chem. Commun.*, 2009, 2290–2292.
- 7 F. Huo, S. Li, Q. Li, Y. Qu and W. Zhang, *Macromolecules*, 2014, **47**, 2340–2349.
- 8 A. Wang, J. Huang and Y. Yan, *Soft Matter*, 2014, **10**, 3362–3373.
- 9 A. H. Groschel, F. H. Schacher, H. Schmalz, O. V. Borisov, E. B. Zhulina, A. Walther and A. H. E. Muller, *Nat. Commun.*, 2012, **3**, 1–10.
- 10 J. F. Lutz and A. Laschewsky, *Macromol. Chem. Phys.*, 2005, **206**, 813–817.
- 11 A. Laschewsky, *Curr. Opin. Colloid Interface Sci.*, 2003, **8**, 274–281.
- 12 Z. Li, E. K. Kesselman, Y. Talmon, M. A. Hillmyer and T. P. Lodge, *Science*, 2004, **306**, 98–101.
- 13 Z. Li, M. A. Hillmyer and T. P. Lodge, *Langmuir*, 2006, **22**, 9409–9417.

- 14 A. Hanisch, A. H. Groschel, M. Fortsch, M. Drechsler, H. Jinnai, T. M. Ruhland, F. H. Schacher and A. H. E. Muller, *ACS Nano*, 2013, **7**, 4030–4041.
- 15 W. Wang, J. Zhang, C. Li, P. Huang, S. Gao, S. Han, A. Dong and D. Kong, *Colloids Surf., B: Biointerfaces*, 2014, **115**, 302–309.
- 16 S. W. Kuo, P. H. Tung, C. L. Lai, K. U. Jeong and F. C. Chang, *Macromol. Rapid Commun.*, 2008, **29**, 229–233.
- 17 S. W. Kuo, P. H. Tung and F. C. Chang, *Eur. Polym. J.*, 2009, **45**, 1924–1935.
- 18 S. W. Kuo, *Polym. Int.*, 2009, **58**, 455–464.
- 19 M. R. Talingting, P. Munk, S. E. Webber and Z. Tuzar, *Macromolecules*, 1999, **32**, 1593–1601.
- 20 J. Zhu and R. C. Hayward, *Macromolecules*, 2008, **41**, 7794–7797.
- 21 Z. Li, M. A. Hillmyer and T. P. Lodge, *Macromolecules*, 2006, **39**, 765–771.
- 22 H. G. Cui, Z. Y. Chen, S. Zhong, K. L. Wooley and D. J. Pochan, *Science*, 2007, **317**, 647–650.
- 23 M. Guo and M. Jiang, *Soft Matter*, 2009, **5**, 495–500.
- 24 A. O. Moughton and R. K. O'Reilly, *J. Am. Chem. Soc.*, 2008, **130**, 8714–8725.
- 25 S. Y. Liu, G. Z. Zhang and M. Jiang, *Polymer*, 1999, **40**, 5449–5453.
- 26 H. Kuang, S. Wu, F. Meng, Z. Xie, X. Jiang and Y. Huang, *J. Mater. Chem.*, 2012, **22**, 24832–24840.
- 27 X. Y. Hu, T. Xiao, C. Lin, F. Huang and L. Wang, *Acc. Chem. Res.*, 2014, **47**, 2041–2051.
- 28 R. Chakrabarty, P. S. Mukherjee and P. J. Stang, *Chem. Rev.*, 2011, **111**, 6810–6918.
- 29 C. H. Lu, C. F. Huang, S. W. Kuo and F. C. Chang, *Macromolecules*, 2009, **42**, 1067–1078.
- 30 Y. C. Wu and S. W. Kuo, *Polym. Chem.*, 2012, **3**, 3100–3111.
- 31 Y. R. Wu, Y. C. Wu and S. W. Kuo, *Macromol. Chem. Phys.*, 2013, **214**, 1496–1503.
- 32 K. W. Huang, Y. R. Wu, K. U. Jeong and S. W. Kuo, *Macromol. Rapid Commun.*, 2013, **34**, 1530–1536.
- 33 Y. C. Wu, Y. S. Wu and S. W. Kuo, *Macromol. Chem. Phys.*, 2013, **214**, 563–571.
- 34 L. Zhang and A. Eisenberg, *Science*, 1995, **268**, 1728–1730.
- 35 L. Zhang, K. Yu and A. Eisenberg, *Science*, 1996, **272**, 1777–1779.
- 36 P. Bhargava, J. X. Zheng, P. Li, R. P. Quirk, F. W. Harris and S. Z. D. Cheng, *Macromolecules*, 2006, **39**, 4880–4888.
- 37 P. Bhargava, Y. Tu, J. X. Zheng, H. Xiong, R. P. Quirk and S. Z. D. Cheng, *J. Am. Chem. Soc.*, 2007, **129**, 1113–1121.
- 38 Y. Mai and A. Eisenberg, *Chem. Soc. Rev.*, 2012, **41**, 5969–5985.
- 39 A. K. Brannan and F. S. Bates, *Macromolecules*, 2004, **37**, 8816–8819.
- 40 P. C. Li, Y. C. Lin, M. Chen and S. W. Kuo, *Soft Matter*, 2013, **9**, 11257–11269.
- 41 H. Shen and A. Eisenberg, *Angew. Chem., Int. Ed.*, 2000, **39**, 3310–3312.
- 42 L. Lei, J. F. Gohy, N. Willet, J. X. Zhang, S. Varshney and R. Jerome, *Macromolecules*, 2004, **37**, 1089–1094.
- 43 J. Ding and G. Liu, *Macromolecules*, 1999, **32**, 8413–8420.
- 44 K. Zhang, L. Gao, Y. Chen and Z. Yang, *J. Colloid Interface Sci.*, 2010, **346**, 48–53.
- 45 C. W. Chiou, Y. C. Lin, L. Wang, T. Hayakawa and S. W. Kuo, *Macromolecules*, 2014, **47**, 8709–8721.
- 46 L. Sun, L. Zhu, L. Rong and B. S. Hsiao, *Angew. Chem., Int. Ed.*, 2006, **45**, 7373–7376.
- 47 C. He, J. Sun, J. Ma, X. Chen and X. Jing, *Biomacromolecules*, 2006, **7**, 3482–3489.
- 48 S. W. Kuo and R. S. Cheng, *Polymer*, 2009, **50**, 177–188.
- 49 Y. C. Wu and S. W. Kuo, *J. Mater. Chem.*, 2012, **22**, 2982–2991.